

Heterogeneous advanced photo-fenton oxidation of phenolic aqueous solutions over iron-containing SBA-15 catalyst

Z. Bailiche^{1,2,3,a}, L. Cherif¹, S. Royer⁴, A. Bengueddach⁵, S. Fourmentin^{2,3} and S. Siffert^{2,3}

¹ *Laboratoire de Catalyse et Synthèse en Chimie Organique, Université de Tlemcen, Algérie*

² *Université Lille Nord de France, 59000 Lille, France*

³ *ULCO, UCEIV, 59140 Dunkerque, France*

⁴ *Institut de Chimie des Milieux et Matériaux de Poitiers IC2MP, Poitiers, France*




⁵ *Laboratoire de chimie des matériaux Université d'Oran, Algérie*

Abstract. Iron-containing SBA15 catalysts have been prepared following different synthesis routes, direct synthesis by adjusting pH at 3 and 6 and with post synthesis procedure. Activity and stability of these materials were assessed on the photo-Fenton degradation of phenolic aqueous solutions by H₂O₂ using near UV irradiation (254 nm) at room temperature and initial neutral pH. Their catalytic performance was mentioned in terms of phenol and total organic carbon (TOC) conversions. Several complementary techniques, including XRD, Nitrogen sorption isotherms, UV visible, were used to evaluate the final structural and textural properties of calcined Fe-SBA15 materials. These materials show a high activity and stability of iron species.

INTRODUCTION

Aromatic compounds are common pollutants in the effluents of several industries. The degradation of these pollutants in wastewater streams has emerged as an important concern during last decade. Advanced oxidation processes (AOPs) such as ozonation, photocatalysis, Fenton and a combination of photo-Fenton, UV/O₃, UV/H₂O₂ have received considerable attention as wastewater treatment processes due to their ability to degrade, and in many cases, mineralize various organic compounds that are otherwise resistant to conventional biological and chemical treatments.

The oxidation system based on the Fenton's reagent (hydrogen peroxide in the presence of ferric ions) has been used as a powerful source of oxidative radicals [1]:



Fenton processes has been shown to be enhanced by light due to the decomposition of the photoactive Fe(OH)²⁺ species, promoting an additional generation of OH radicals in solution [2]:



However, in order to overcome some drawbacks of this process (acidic pH requirement: pH = 2–4), loss of Fe ions in water, etc., heterogeneous Fenton type systems have been synthesized to catalyze various organic compounds in mild reaction conditions.

^a e-mail: bz3946@yahoo.fr

The unique characteristics of mesoporous molecular sieves, such as high surface area, large pore volume and well defined pore size, make the material potential in catalysis, adsorption, etc.

However, few investigations have been reported in using mesoporous materials for heterogeneous Fenton oxidation [3–6]. The purpose of this study is the assessment of Fe-containing SBA-15 mesostructured materials prepared by direct synthesis (by adjusting the pH at 6 and 3) and post synthesis procedures for the heterogeneous photo-Fenton degradation of phenolic aqueous solutions. Activity and stability of these materials have been evaluated according to the Si/Fe ratio 20 and 60.

EXPERIMENTAL

A detailed synthesis procedure for mesoporous silica SBA-15 has been reported elsewhere [7]. Iron substituted mesoporous SBA15 molecular sieve has been prepared by direct synthesis at pH = 3 and 6 and post synthesis procedures using iron nitrate as source of iron.

Direct synthesis: Fe-SBA-15 materials synthesized at pH 3 were prepared as follows: 4.0 g triblock copolymer poly(propylene oxide)-poly(ethylene oxide) (EO20PO70EO20 Pluronic 123 from Aldrich) was dissolved in 30.0 g of water and stirred for 4 h at 40 °C. 9.0 g of orthosilicate (TEOS) and the appropriate amount of iron nitrate were added directly to the homogeneous solution (Si/Fe = 20 and 60). Then appropriate quantity of 0.3 M HCl was added to adjust the pH value of mixture at 3.

The gel was stirred for 24 h and then maintained at 100 °C in a Teflon-lined autoclave for another 48 h. The resultant precipitate was collected, washed thoroughly with distilled water; template removal was achieved by calcination in air at 500 °C for 4 h (heating rate: 1 °C/mn).

Fe-SBA-15 materials synthesized at pH 6: 4.0 g triblock copolymer poly(propylene oxide)-poly(ethylene

Table 1. Physical properties of the calcined FeSBA15.

Sample	SBA-15	Fe/SBA-15		Fe-SBA-15 pH6		Fe-SBA-15 pH3	
	/	20	60	20	60	20	60
d ₁₀₀ (Å)	96	103.8	101.4	91.9	101.5	92.3	103.7
a (Å)	110.8	119.9	117.1	106.1	117.2	106.6	119.7

oxide) (EO₂₀PO₇₀EO₂₀Pluronic 123 from Aldrich) was dissolved in 40 ml 2M HCl and stirred for 30 mn at 40 °C. 9.0 g of orthosilicate (TEOS) was added to the homogeneous solution Then appropriate quantity of 2M NH₄OH were added to adjust the pH value of mixture to 6, then the appropriate amount of iron nitrate were added directly to the homogeneous solution in order to obtain a well defined Si/Fe = 20 and 60. The gel was stirred for 2 h and then maintained at 100 °C in a Teflon-lined autoclave for three days.

The resultant precipitate was collected, washed thoroughly with distilled water; template removal was achieved by calcination in air at 500 °C for 4 h (heating rate: 1 °C/mn). The samples were called Fe-SBA-15 (n) where n represented the Si/Fe ratio.

Post-synthesis: the calcined SBA-15 (0.5 g) was dispersed in 50 ml of deionised water containing various amounts of iron nitrate, in order to obtain a well defined Si/Fe ratio equal to 20 and 60. The resulting mixture was stirred at room temperature for 12 h and the powder was filtered, washed with deionised water and dried at room temperature in air. The samples were called Fe/SBA-15 (n).

Various techniques including XRD, N₂ adsorption and diffuse reflectance UV-Vis (DR-UV-Vis) were employed for the materials characterization.

Heterogeneous photo-Fenton reaction were carried out in a cylindrical pyrex reactors with one central and three peripheral female conical connections for the inflow and outflow of the solution model using phenol as reactant and hydrogen peroxide as oxidant.

The catalyst (100 mg) was put into 100ml of an aqueous phenol solution (5×10^{-4} mol L⁻¹) and the required amount of H₂O₂ was used for a complete phenol oxidation.




The reaction was carried out in ambient conditions (atmospheric pressure, 25 °C and at neutral pH).

A dark Fenton were performed in atmospheric pressure, 25 °C and the pH of the reaction was maintained at 3.

Phenol conversions were determined by High performance liquid chromatograph (HPLC, Waters 600) equipped with a C-18 column at a rate of 1 ml /min with UV detection with amobile phase of 20% acetonitrile and 80% H₂O.

Iron leaching was systematically evaluated by ICP analyses model (820 MS Varian) after catalytic tests.

Totalorganic carbon (TOC) content of the solutions after reaction was analyzed using a Shimadzu TOC-VCSH analyzer.

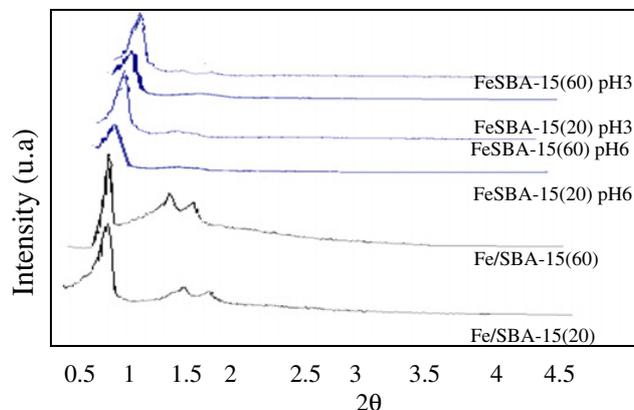**Figure 1.** XRD profiles of FeSBA15.

RESULTS AND DISCUSSION

Small angle X ray diffraction patterns of the Iron-containing SBA-15 materials are shown in Fig. 1. These materials exhibit a low angle reflections indexed as (100), (110) and (200) which can be associated with the hexagonal symmetry characteristic of mesoporous SBA-15. We can note that co-condensed materials (Fe-SBA-15) are not as highly ordered as impregnated materials Fe-SBA-15. The XRD patterns of Fe-SBA-15 show that the peaks (110) and (200) are not well resolved whatever the synthesis pH value and Si/Fe ratio. This could be explained by the lattice distortion after insertion of Fe. Since the radius of the ionic Fe³⁺ ($r_{\text{Fe}^{3+}} = 0.63 \text{ \AA}$) is larger than that of Si⁴⁺ ($r_{\text{Si}^{4+}} = 0.40 \text{ \AA}$), the increase in the unit cell parameter value of the Fe-SBA-15 (60) material (Table 1) may indicate that Fe³⁺ ions are incorporated into the frame work of the SBA-15 material; generally, it is expected that the unit cell parameter will be enlarged after the incorporation of metal cations with ionic radius larger than that of Si⁴⁺. However the Fe rich containing SBA15 (Fe-SBA-15 (20)) presents a decrease in its unit cell parameter; this result could be attributed to a partial collapse of hexagonal porosity caused by the modification induced by the iron introduction in the mesoporous silica structure [8,9].

In all cases, the absence of diffraction peaks at $2\theta > 10^\circ$ seems to exclude the presence of Fe₂O₃ crystallites or in too low quantity to be observed.

Typical irreversible type IV adsorption isotherms as defined by IUPAC [10] were observed which is typical of mesoporous materials. The N₂ isotherms remained unchanged in shape for impregnated materials Fe/SBA15 and co-condensed materials (Fe-SBA15) at pH = 6 compared to that of SBA15. By contrast, the N₂ isotherms were less sharp for co-condensed materials


Table 2. Specific surfaces of FeSBA-15 compounds.

Sample	Fe/SBA-15		Fe-SBA-15pH6		Fe-SBA-15pH3	
Si/Fe	20	60	20	60	20	60
S _{BET} (m ² /g)	732	601	822	623	502	895

Table 3. Activity of catalysts FeSBA-15.

Sample	t (min)	X _{Phenol} (%)	Leaching ^a %	X _{TOC} (%)
Fe/SBA-15 (20)	0	0	33.3	13.3
	5	93.9		
	10	98.7		
	15	100		
Fe/SBA-15 (60)	0	0	11.8	16.3
	5	84.0		
	10	96.2		
	15	100		
Fe-SBA-15 (20) pH6	0	0	22.5	5.3
	5	90.5		
	10	100		
	15	100		
Fe-SBA-15 (60) pH6	0	0	15.9	7.3
	5	90.0		
	10	100		
	15	100		
Fe-SBA-15 (20) pH3	0	0	17.0	11.4
	5	90.7		
	10	100		
	15	100		
Fe-SBA-15 (60) pH3	0	0	15.0	9.6
	5	79.2		
	10	96.7		
	15	100		

a: Percentage from leaching iron leached from the catalyst.

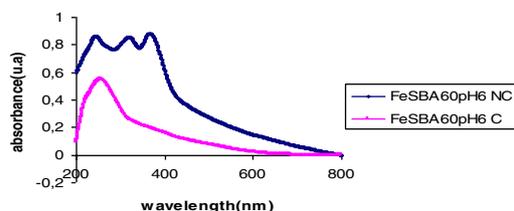
Figure 2. The diffuse reflectance UV-visible spectra of Fe-SBA15.

(Fe-SBA15) at pH = 3 indicating that the materials were less ordered and uniform compared to SBA15.

The BET surface area values of FeSBA-15 materials are listed in Table 2. SBA-15 sample exhibits a specific surface area of 930 m²/g. A decrease in specific surface area is logically observed after iron incorporation [5].

Diffuse reflectance UV-vis spectroscopy was used to investigate the nature the Fe (III) species. The DR-UV-vis spectra of as synthesised and calcined FeSBA15 samples are shown in Figure 2.

The spectra of as synthesised Fe-SBA15 (Si/Fe = 20 and 60) synthesized at pH = 6 show two absorption bands below 250 nm (210 nm, 240 nm), two bands between 300 and 400 nm. The bands below 250 nm are attributed to isolated Fe³⁺ in tetrahedral coordination and those

between 300 and 400 nm are attributed to iron oxide nanoclusters (Fe_xO_y) [11]. Both samples are free of large Fe₂O₃ as evidenced by missing bands above 400 nm.

The DR-UV-Vis spectra of calcined Fe-SBA-15 samples synthesized at pH = 6 show the exaltation of the band attributed to Fe³⁺ in tetrahedral coordination (< 250 nm), disappearance of bands attributed to nanoclusters of iron oxide (300–400 nm) and the appearance of a band at 250 nm (< 300 nm) attributed to Fe³⁺ in octahedral coordination. This result can be explained by the redispersion of the iron species and their partial insertion into the frame work after calcination of the Fe-SBA-15 materials. The insertion of iron into the framework after calcination is in contradiction with what is usually observed with mesoporous materials exchanged by metal.

The spectra of as synthesised and calcined Fe-SBA-15 (Si/Fe = 20) synthesized at pH = 3 show two absorption bands; the first is attributed to Fe³⁺ in tetrahedral coordination (< 250 nm) and the second is attributed to nanoclusters of iron oxide (300–400 nm).

Activity and stability of catalytic systems in photoassisted oxidation of phenolic aqueous solutions

Table 3 summarizes the activity of all the catalysts prepared during this study in the photo-Fenton of phenol

degradation at different reaction times. A nearly total phenol removal is displayed by all samples after reaction times of 10 min. Table 3 shows the effect of Si/Fe ratio and the synthesis procedure of FeSBA-15 on phenol degradation, suggesting in the case of Fe-SBA-15 synthesized at pH3 that the decrease in Si/Fe from 60 to 20 accelerate the oxidation of phenol since more radicals are produced from higher iron loaded catalysts according to the Eqs. (1–4). However, in the case of Fe-SBA-15 synthesized at pH6 and Fe/SBA-15 synthesized by post-synthesis procedure, the oxidation of phenol is not accelerated with the decrease in Si/Fe from 60 to 20; Therefore Si/Fe = 60 is the optimum value and 100% of phenol has been degraded after reaction time of 10 min with Fe-SBA-15 synthesized at pH6. It has been demonstrated that the photo-Fenton activity of a catalyst can be influenced by its surface area, crystal structure, particle size distribution or surface hydroxyl group density [12].

If we compare the values of TOC conversion we observed a high activity for the catalyst Fe-SBA-15 synthesized at pH6.

An important point in the design of heterogeneous catalytic systems for advanced oxidation processes is the resistance of metal species to be leached into the aqueous solution under the oxidant; in this sense, stability of all the materials was evaluated in the terms of the percentage of iron leached from the catalyst with the reaction time. The catalyst Fe/SBA-15 (20), synthesized by post-synthesis procedure, shows a higher leaching degree in comparison to those obtained by direct synthesis, which are mainly composed of framework iron which is more resistant to be leaching out into the aqueous solution.

Study of parallel reactions on the phenol photo-degradation

The influence of parallel reactions such as dark-Fenton, degradation mediated by photolysis of H₂O₂ and adsorption phenomenon on the overall degradation of phenol has been studied. The results show that mineralization of phenol towards carbon dioxide and water by irradiated homogeneous Fenton catalytic systems and UV/H₂O₂ processes may occur along with heterogeneously Fenton photo-assisted reactions, but the remarkable contribution of iron containing SBA-15 catalyst is undoubtedly demonstrated.

Study of stability of catalysis

The performance of Fe-SBA-15 (60) synthesized at pH6 in phenol degradation after catalyst recycling with filtration and water washing is similar to the first test; this

suggests the stable performance of Fe-SBA-15 (60) in heterogeneous Fenton oxidation.

CONCLUSION

A series of iron-based mesoporous materials were prepared following different routes. Fe-SBA15 prepared by direct synthesis are not as highly ordered as impregnated materials Fe/SBA-15. It's worth noting that after calcination of Fe-SBA-15 synthesized at pH6, the extra framework iron species are redispersed and partially inserted into the framework. Activity and stability of FeSBA-15 for treatment of phenolic aqueous solutions depend on the synthesis strategy and Si/Fe ratio.

Fe-SBA-15 (60) synthesized at pH6 is a promising catalyst for photo-Fenton processes.

The authors are grateful to PHC Maghreb n°27959PD for financial support.

References

- [1] C. Walling, A. Goosen, *J. Am. Chem. Soc.* 95, 2987–2991, 1973.
- [2] V. Nadochenco, J. Kiwi, *Inorg. Chem.* 37, 5233–5238, 1998.
- [3] N. Gokulakrishnan, A. Pandurangan, P. K. Sinha, *J. Chem. Tech. Biot.*, 82, 25–32, 2007.
- [4] F. Martinez, G. Calleja, J. A. Melero, R. Molina, *Applied Catal. B: Environmental*, 60, 181–190, 2005.
- [5] L. Xiang, S. Royer, H. Zhang, J. -M. Tatibouët, J. Barrault, S. Valange, *J. Hazard. Mater.*, 172, 1175–1184, 2009.
- [6] P. Shukla, S. Wang, H. Sun, H. M. Ang, M. Tadó, *Chem. Eng. J.*, 164, 255–260, 2010.
- [7] D. Zhao, J. Feng, Q. Huo, N. Melosh, G.H. Frederickson, B.F. Chmelka, G. D. Stucky, *Science*, 279, 548, 1998.
- [8] Z. EL Berrichi, L. Cherif, O. Orsen, J. Fraissard, J.P. Tessonnier, E. Vanhaecke, B. Louis, M.J. Ledoux, C. Pham-Huu, *Appl. Catal. A*, 298, 194, 2006.
- [9] C.F. Cheng, M.D. Albo, J. Klouski. *Chem. Phys. Lett.*, 250, 328, 1996.
- [10] IUPAC Manual of Symbols and Terminologie, Appendix 2, Part 1 Colloid and Surface Chemistry, *Pure. Appl. Chem*, 1972, 31, 578.
- [11] S. Bordiga, R. Buzzoni, F. Geobaldo, C. Lamberti, E. Giamello, A. Zecchina, G. Petrini, G. Tozzola, G. Vlaic, *J. Catal.*, 158, 486, 1996.
- [12] D.W. Bahnemann, in: E. Pelizzetti, M. Schiavello (Eds.), *Kluwer Academic Publishers, Dordrecht*, p. 251, 1991.