

Cyanide Containing Wastewater Treatment by Ozone Enhanced Catalytic Oxidation over Diatomite Catalysts

Mingguo Lin¹, Qiuyan Gu², Xinglan Cui² and Xingyu Liu^{2*}

¹Liaoning Xindu Gold Co., Ltd, 122000 Chaoyang, China

²General Research Institute for Nonferrous Metals Engineering, National Engineering Laboratory of Biohydrometallurgy, 100088 Beijing, China

The first two authors contributed equally to this paper

Abstract. Cyanide containing wastewater that discharged from gold mining process creates environmental problems due to the toxicity of cyanide. As one of the promising advanced oxidation process, catalytic oxidation with ozone is considered to be effective on the purification of cyanide. Diatomite, a natural mineral, was used as catalyst in this study. The effect of O₃ dosage, salinity, initial cyanide concentration and initial pH condition were investigated. It was observed that the removal rate of cyanide was much higher in the catalytic oxidation with ozone process than the one in zone alone process. Alkaline condition was especially favorable for cyanide in catalytic oxidation with ozone. The ozone and catalytic oxidation with ozone were simulated by pseudo-first-order kinetics model. The apparent first-order rate constant contribution of the diatomite catalyst was 0.0757 min⁻¹, and the contribution percentage was 65.77%.

1 Introduction

Cyanidation is the most popular process by which gold is recovered from the ores in mining operations. The aqueous cyanide solution which is used to dissolution of gold is typically carried out with 0.03-0.3% NaCN [1]. The cyanide in the solution is used as complexing agent. However, after extraction and recovery of gold, the drainage containing large amounts of cyanide need be discharged, which create environmental problems due to the toxicity of cyanides [2].

The cyanide could present three forms in wastewater, including free cyanide, simplex cyanide and complex cyanide. For the widespread use of cyanide in gold mining operation, the purification of cyanide is important. Both treatment efficiency and cost could be considered [3]. The Ministry of Environmental Protection of the People's Republic of China has proposed a discharge limit of 0.5 mg/L cyanide for sewers. And in Liaoning Province, the limit for cyanide is 0.2 mg/L. For meeting the strict discharge standard requirement, several cyanide treatment processes have been developed.

* Corresponding author: wellwoodliu@163.com

Catalytic oxidation with ozone is one of the promising treatment techniques for cyanide removal. Ozone has been demonstrated to be effective on the purification of non-biodegradable compounds, by the way of direct oxidation with O₃ and the indirect way with hydroxyl radicals [4].

In the last years, the combined use of O₃ and activated carbon has been developed [5]. The treatment efficiency was enhanced dramatically by using activated carbon as catalyst [6]. Unfortunately, the cost of activated carbon is expensive, which is limited the application of the combined process. Diatomite could be the substitute catalyst which has porous structure and high surface area. In this study, the operating parameter of combined O₃ and diatomite were optimized.

2 Materials and methods

2.1 Wastewater

The real cyanide containing wastewater was captured from a gold mine company in Liaoning Province. The cyanide concentration is 15~20 mg/L, and COD concentration is 150~200 mg/L.

2.2 Analyses

The concentrations of cyanide were measured by using an ion selection electrode. COD was measured according to standard methods. The microstructure of diatomite was observed by scanning electron microscope (ZEISS EVO 18). The increase in apparent rate constant (pseudo-first-order) K_{app} resulted from adding diatomite during the ozone process can be used to indicate the contribution and contribution percentage of effect of diatomite catalyst, which was calculated as the following equation:

$$\text{Contribution } K_{app} = K_{app}(\text{with diatomite}) - K_{app}(\text{without diatomite}) \quad (1)$$

$$\text{Contribution percentage} = (1 - K_{app}(\text{without diatomite})/K_{app}(\text{with diatomite})) \times 100\% \quad (2)$$

The pseudo-first-order kinetics of both processes was simulated as:

$$\ln(C_0/C) = K_{app}t \quad (3)$$

Where C is the cyanide concentration at time t, C₀ is the initial cyanide concentration, and K_{app} is the apparent first-order rate constant.

2.3 Experimental method

The schematic diagram of combined ozone and diatomite system is shown in Fig.1. Two parallel set of ozone reactor, named R1 and R2, were operated concurrently. R2 was similar with R1 except adding diatomite. R1 and R2 reactor were made by borosilicate glass. Ozone was continuously added to the reactor.

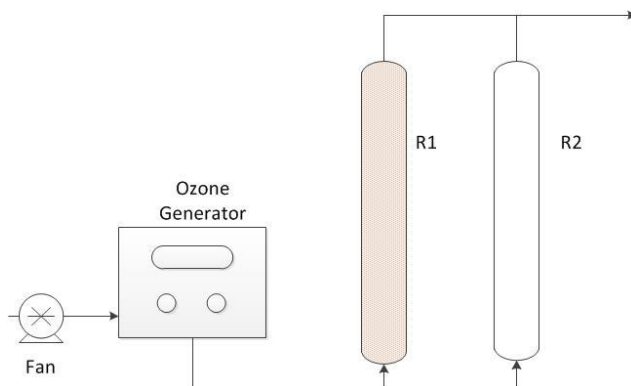


Fig. 1. Schematic diagram of combined ozone and diatomite system.

3 Results and discussion

3.1 Micro-morphology observation of diatomite

The electronic micrograph of diatomite was shown in Fig. 2. The diatomite has high porosity which could provide the site to promote the reaction between O_3 and cyanide.

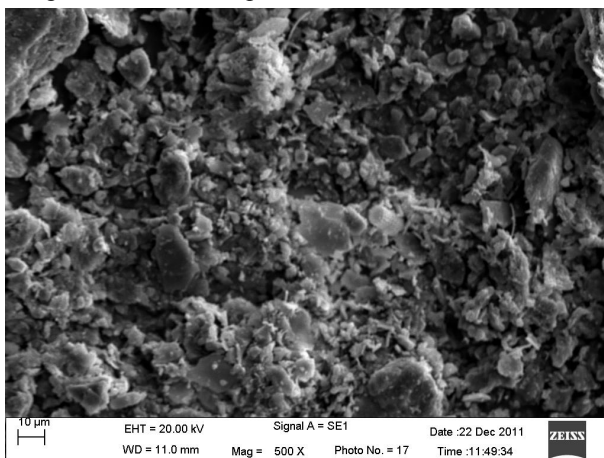


Fig. 2. Scanning electron micrographs for diatomite.

3.2 Effect of O_3 dosage

Fig.3 shows the cyanide concentration as a function of O_3 dosage. The results indicated the combined O_3 and diatomite process presented better cyanide purification performance than the O_3 alone process. Cyanide concentration in R1 decreased from 15.8 mg/L to 0.1 mg/L with an increase in the O_3 dosage to 16 mg/L, while the cyanide concentration in R2 dropped to 6.3 mg/L.

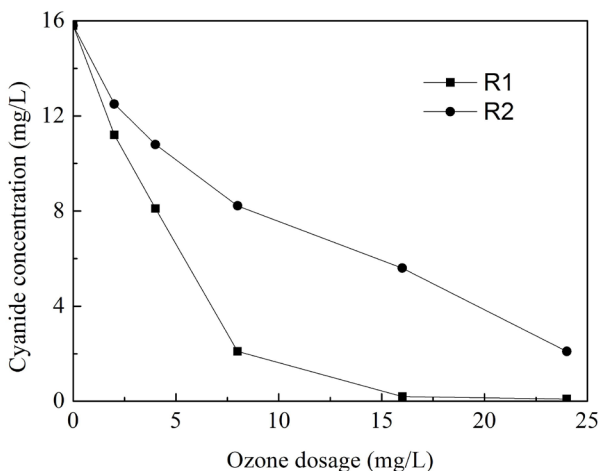


Fig. 3. Effect of O₃ dosage on the removal of cyanide.

3.3 Effect of salinity

Salinity always influences the catalytic oxidation via the competitive adsorption of inorganic anions on catalyst sites. The influence of NaCl was investigated during catalytic oxidation with ozone. The effect of NaCl is shown in Fig. 4, in which a series amount of NaCl (0, 0.5 g/L, 1 g/L) was added in the oxidation system. It is observed that the salinity did not influence the catalytic oxidation significantly. The real industrial wastewater always contains high salinity. The results indicated that the catalytic oxidation with ozone process could be suitable for the treatment of industrial wastewater.

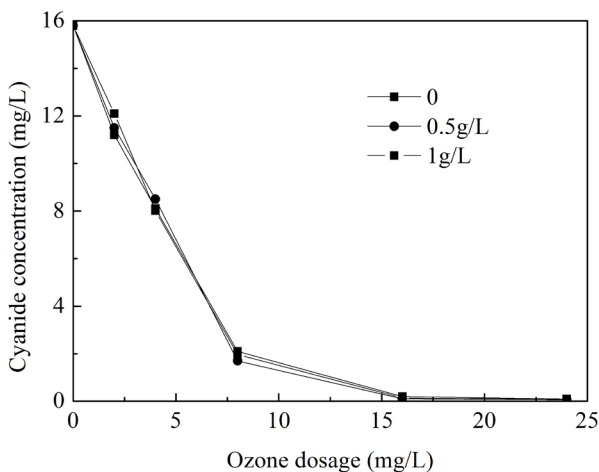


Fig. 4. Effect of salinity on the removal of cyanide.

3.4 Effect of initial pH

Cyanide containing wastewater could influence the charge property of cyanide and removal efficiency of ozone process. The effect of cyanide containing wastewater pH on the treating rate was investigated from 5.0 to 9.0. As illustrated in Fig.5, the fastest cyanide removal rate was observed in the condition of pH 9.0, while the slowest was demonstrated in the condition of pH 5.0. The acid solution condition could not promote the reaction activity between O₃ and cyanide. These observation also indicated that at high pH the hydroxyl radical could be the predominant oxidant for the cyanide. The product of cyanide oxidation is cyanate, which occurs according to Eq(4):



In the mostly alkaline solutions hydrolysis of CNO⁻ is also possible:

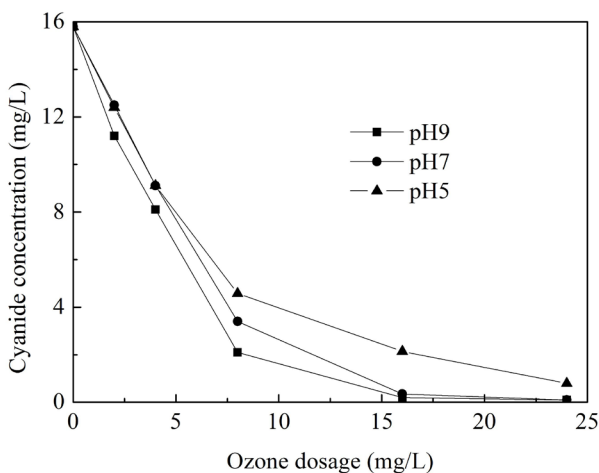



Fig. 5. Effect of pH on the removal of cyanide.

3.5 Effect of initial cyanide concentration

The tests of difference initial cyanide concentrations were carried out (Fig. 6). When the initial cyanide concentration was 15.8 mg/L, 16 mg/L O₃ was needed to add into the solution. The initial cyanide removal rate decreased with the drop of the initial cyanide concentration. High initial cyanide concentration could promote the oxidation reaction. The increased initial cyanide concentration provided more drive force to transfer cyanide to diatomite surface. Therefore, the hydroxyl radicals generated by ozone could react with more cyanide.

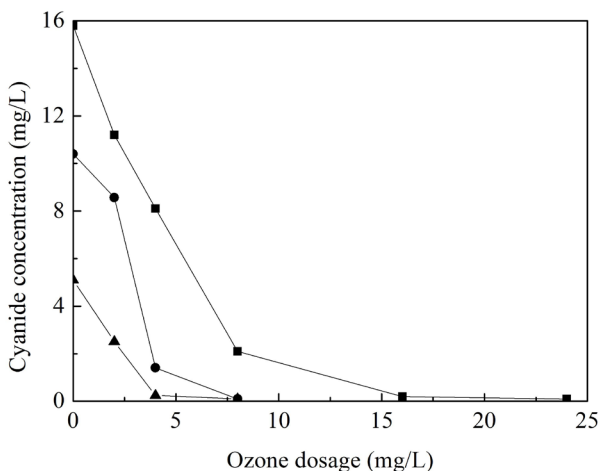


Fig. 6. Effect of initial concentration on the removal of cyanide.

3.6 Kinetics analysis

The pseudo-first-order kinetics was used to simulate the cyanide degradation data. Fig.7(a) shows the change trend of cyanide removal efficiency vs time. The apparent first-order rate constants of cyanide oxidation were determined from the slope of the straight lines obtained by plotting the ratios of the remaining concentration to the initial concentration on logarithmic scale. As shown in the Fig. 7(b), the data could fit the pseudo-first-order kinetics model very well. It is also evident from Fig. 7(b), that the behavior of cyanide oxidation identified a pseudo-first-order reaction with respect to cyanide concentration in solution. The apparent first-order rate constant of the ozone oxidation without diatomite is 0.0394 min⁻¹, and regression R² is 98.41%, while the one with diatomite is 0.1151 and 98.07%. The cyanide oxidation was enhanced by adding diatomite as catalyst. The catalyst of diatomite during the ozone oxidation plays a significant role during the process. The K_{app} contribution in the present of diatomite was 0.0757 min⁻¹, and the contribution percentage of adding diatomite was 65.77%.

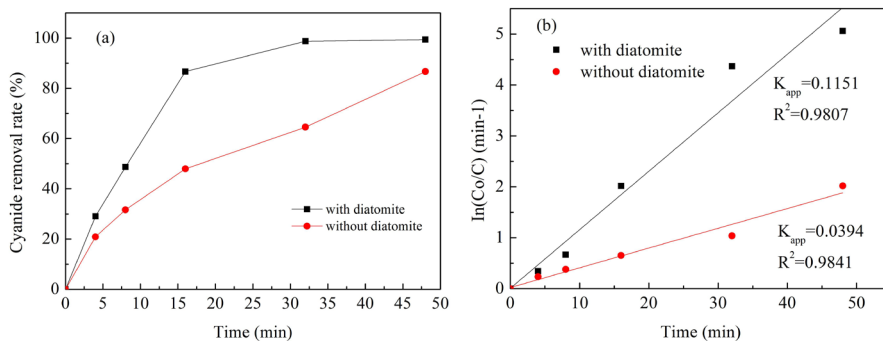


Fig. 7. Pseudo-first-order kinetics modeling: (a) trend of cyanide removal efficiency vs time, (b) correlation between experimental data (points) and prediction curves (line).

4 Summary

During cyanide oxidation by catalytic oxidation with ozone, the contribution and contribution percentage of diatomite which was used as catalyst were investigated by comparison with single ozone process. The apparent first-order rate constant contribution of the diatomite catalyst was 0.0757 min^{-1} , and the contribution percentage was 65.77%. In addition, the effect study of O_3 dosage, salinity, initial cyanide concentration and initial pH condition were carried out. It was observed that alkaline condition was especially favorable for cyanide in catalytic oxidation with ozone. And the solution salinity did not influence the catalytic oxidation effect. These results indicated that catalytic oxidation with ozone is effective on the purification of cyanide.

This work was supported by the fund of General Research Institute for Nonferrous metals under grant numbers 53321 and 53348, and the public welfare fund of the Ministry of Environmental Protection of People's Republic of China under grant number 201509049, the National Natural Science Foundation of China under grant numbers U1402234, 41573074.

References

1. J. A. Zeevalkink, D. C. Visser, P. Arnoldy, C. Boelhouwer, *Wat. Res.* **14**, 1375 (1980)
2. J. R. Parga, D. L. Cocke, *Desalination* **140**, 289 (2001)
3. U. Kepa, E. S. Mazanek, L. Stepniak, *Desalination*, **223**, 187 (2008)
4. M. D. Gurol, R. Vatistas, *Wat. Res.* **21**, 895 (1980)
5. F. R. Carrillo-Pedroza, F. Nava-Alonso, A. Uribe-Salas, *Miner. Eng.* **13**, 541 (2000)
6. J. Cui, X. Wang, Y. Yuan, X. Guo, X. Gu, L. Jian, *Chem. Eng. J.* **241**, 184 (2014)