

Removal of Copper (II) Ions in Aqueous Solutions by Sorption onto Alkali Activated Fly Ash

Lita Darmayanti^{1,2,*}, Suprihanto Notodarmodjo¹, Enri Damanhuri¹, and Rino R Mukti³

¹ Environmental Engineering Department, Institut Teknologi Bandung, Jalan Ganesha No. 10 Bandung 40132, Indonesia

² Civil Engineering Department, Universitas Riau, Kampus Bina Widya Simpang Baru, Pekanbaru Riau 28293, Indonesia

³ Chemistry Department, Institut Teknologi Bandung, Jalan Ganesha No. 10 Bandung 40132, Indonesia

Abstract. Fly ash is a particulate material produced from coal combustion power plants with major components are silica, alumina, iron oxide, calcium oxide, magnesium oxide, and carbon which are ideal for metal adsorbents. The potential use of fly ash in the wastewater treatment process is obvious because it can be obtained cheaply in large quantities and it can be used as an adsorbent. However, fly ash still shows lower adsorption capacity unless it is activated. In this study, fly ash activated by NaOH 14 M and KOH 14 M solutions. The batch experiments were carried out to study the sorption of copper ions from aqueous on alkali activated fly ash. The influence of initial concentration and contact time were examined at constant pH and dose of adsorbent. The sorption capacity of copper ions increased with the initial concentration and contact time. The sorption capacities followed the order Na1>Ka1>FA. The adsorption isotherm model exhibited that the Langmuir model is very suitable with copper ions adsorption onto fly ash and alkali activated fly ash. Kinetic study shows that adsorption of copper ions onto FA, Na1, and Ka1 follows the pseudo second-order kinetics.

1 Introduction

Rapid industrialization and economic development cause heavy metals to be introduced to environment continuously through point and non-point sources. Heavy metals are generated as a rest of metal refinishing products. Therefore, heavy metals pollution is still an environmental problem nowadays in whole of countries. Heavy metals are becoming a public health problem since these elements do not degrade and tend to accumulate in living organism, causing various diseases and disorders. Some of metals like Hg, Pb, and Cr can become very toxic to organism, others like Fe, Mn, Cu, Zn, Ni and Co though essential for living beings, when present in excess certain limits can be very harmful. Copper is highly toxic because it is bioaccumulative, persistent which does not break down in the environment and carcinogenic [1-3].

There are various treatment processes available for treatment metal-contaminated water, such as, chemical precipitation, coagulation, oxidation with ozone/hydrogen peroxide, ion exchange, photo catalytic degradation, and adsorption [4]. Among of these methods, adsorption appears to be the most widely used for the removal of heavy metals [5]. There are many low-cost material have been investigated for removal of heavy metals from water such as hardwood and corn straw [6], oil shale ash [7], carrot residues [8], *Lonicera japonica* flower biomass [9] and lignin [10,11].

Fly ash is a particulate material produced from coal combustion power plants that requires ultimate disposal. The major components of fly ash are silica, alumina, iron oxide, calcium oxide, magnesium oxide, and carbon which are ideal for metal adsorbents. The potential use of fly ash in the wastewater treatment process is obvious because it can be obtained cheaply in large quantities and it can be used as an adsorbent and as a neutralization agent [12]. Several research reported that significant amounts of heavy metals were removed from solution by adsorption onto fly ash. Sharma [13] studied the removal of chromium from aqueous solutions and wastewaters, Polowczyk [14] examined the efficiency of fly ash agglomerates (particles size 1.0-1.6 mm) for removal of boron from aqueous solution.

However, fly ash still shows lower adsorption capacity unless it is modified. Alkali activation is a technology that can enlarge utilization of fly ash. The alkali activation or geopolymerization formed of mixing the fly ash with alkaline activators and then curing the paste at a certain temperature to result a solid material [15]. Alkali activated fly ash have been more widely used for cement replacement. Nowadays, alkali activated fly ash also used as adsorbent for removal heavy metals with higher adsorption capacity [1, 17-18]. The objective of this study is to investigate the effectiveness of alkali activated fly ash for removal copper ion from aqueous solution using batch experiment to determine adsorption kinetic and isotherm.

* Corresponding author: litadarmayanti@eng.unri.ac.id

2 Experimental

2.1 Materials

A sample of the raw fly ash was collected from a coal-firing power plant of PT Trisula Textile, in Bandung city, Indonesia. This material sieved to a particle sizes less than 0,074 mm (sieve no. 200). All chemical were analytical grade reagents supplied by Merck. Solutions containing copper ions were prepared by dissolving the appropriate weight of $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ in distilled water.

2.2 Alkali activation of fly ash

Treatment method involved mixed the certain amounts of fly ash with two different alkaline activator, NaOH 14 M and KOH 14 M. Liquid/solid ratio was 0.6. After adding all the component, the mixture was mixed for 15-20 min and poured into polypropylene bottles. Bottles were closed to prevent moisture evaporation. The fresh pastes were heat at 85°C for 24 h in an oven. After that, geopolymer were removed from oven and kept at room temperature for 3 days. Activated fly ash bodies were washed with acetone to remove the excess of alkaline activator and then crushed, sieved to obtain particle diameter less than 0.074 mm, and stored in a desiccator prior to use.

2.3 Sorption experiments

The sorption of copper ions on raw fly ash and activated fly ash adsorbent were studied by shaking 0.1 L of varying Cu concentration from 5-60 mg/l at temperature of 25°C with a constant amount of adsorbent (0.15 g) in batch reactors. The mixtures were shaking with horizontal shaker at 250 rpm for 60 min. The concentration of the copper ions in the filtered sample was determinate by atomic absorption spectrophotometer. Duplicate batch were applied for all experiment and mean values were used.

3 Results and Discussion

3.1 Characterisation of adsorbents

The BET surface areas and pore volumes of fly ash and activated fly ash were obtained from N_2 adsorption and given in Table 1. The fly ash has the lowest surface area and pore volume. Activated fly ash with alkaline activator produces materials with higher surface area and pore volume.

Table 1 Textural properties of fly ash and activated fly ash

Sample	S_{BET} (m^2/g)	V (cm^3/g)
Fly ash	9.5	0.022
FA-NaOH	21.9	0.052
FA-KOH	23.0	0.055

Fly ash is an essentially vitreous material (halo recorded at $2\theta=15-35^\circ$) that also contains a series of

minority crystalline phase like Q, M, and H. Activation of fly ash with different solutions change the diffraction pattern. It has to be highlighted the shift in the position of the halo attributed to the vitreous Phase in the initial ash to slightly higher angular values ($2\theta=20-40^\circ$). The changes indicate the formation of an alkaline aluminosilicate gel (Fig. 1).

The original fly ash peaks of quartz, mullite, and hematite were also found in the samples of activated fly ash. However, these peaks tended to lose their intensity. This finding suggest that reactions disorganized the structure of the crystalline of the fly ash particles (Q, M, H) produced by the alkaline activator. There was also an increase in the number of crystalline compounds which demonstrated on the formation of new crystalline compounds (albite and nahcolite).

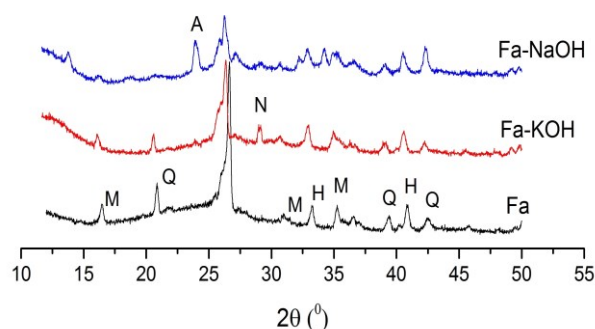


Fig. 1 XRD patterns of fly ash and alkali activated fly ash

The change in morphology of the original surface of the FA particles, can be explained by the dissolution of the vitreous aluminosilicate phase in the raw FA and the crystallization of zeolitic materials onto the external surface of FA particles as pseudomorphs, taking into account that the zeolitic aggregates keep the original shape of the FA spheres after alkaline activation (Fig. 2).

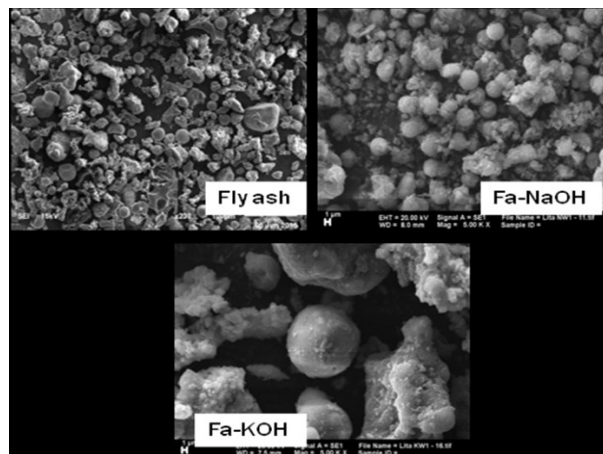


Fig. 2 SEM images of fly ash and synthesis products

3.2 Factors affecting Cu^{2+} adsorption

The removal of Cu onto fly ash activated by NaOH (Na1), KOH (Ka1), and raw fly ash (FA) as a function of the their concentrations was studied under the following conditions: pH: 4; adsorbent dose: 1,5 g/l, temperature: 25°C, equilibrium time: 60 min, and initial

concentrations ranging from 5-60 mg/l. Percentage of Cu²⁺ removal were compared (Fig. 3).

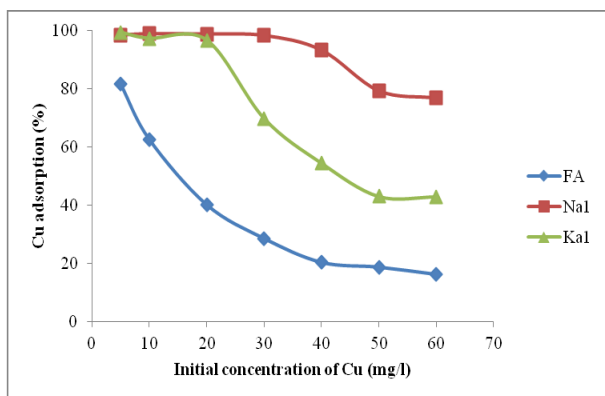


Fig. 3 Effect of initial concentration on Cu removal efficiency

Percentage of adsorption decreases with increasing initial concentration in aqueous solutions. The removal of Cu decreases from 81 to 16%, from 99 to 77%, and from 99 to 43% by adsorption onto FA, NaI, and KaI respectively by increasing concentration from 5 to 60 mg/l. Percentage removal of Cu was increased when fly ash activated by NaOH and KOH. This results indicate that adsorption percentage of NaI is higher than KaI.

The Cu uptake may be attributed to different mechanisms of ion exchange process as well as to adsorption process. During the ion exchange process, metal ions move through the pores of the alkali activated fly ash mass and channels of the lattice and then they replace exchangeable cations (Na and K). Diffusion was faster through the pores and was retarded when it moved through the smaller diameter channels. In this study, the Cu uptake could mainly be attributed to ion exchange in microporous of alkali activated fly ash.

The effect of contact time on Cu²⁺ ions removal was conducted at initial concentration 50 mg/l, adsorbent dose 1,5 g/l, value of pH 4, temperature 25°C, and contact time varying from 5 to 120 min. the results are shown in Fig. 4.

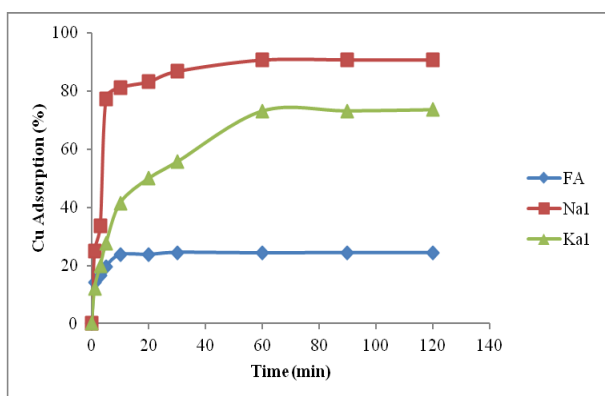


Fig. 4 Effect of contact time on Cu removal efficiency

The sorption of Cu²⁺ ions onto alkali activated fly ash is depended on time. A significant removal of Cu²⁺ occurs after 10 min contact time (23%, 81%, and 42% for Fa, NaI, and KaI respectively) and only change slightly in removal efficiency occurred after this period

of time. The results ensured that the removal of Cu²⁺ from the aqueous solution had occurred under equilibrium conditions. As expected, the using of alkali activated pretreatment will increase adsorption performance of Cu²⁺ onto fly ash. Adsorption of Cu²⁺ by sorbent that developed in this study is relatively fast and 60 min contact time is sufficient to reach the adsorption equilibrium and this contact time was applied in following test.

3.2 Adsorption isotherm

Adsorption isotherms are essential to explore the nature interaction between metal ion with adsorbent. The adsorption data have been analysed with two adsorption isotherm methods which are Langmuir and Freundlich equations [19].

3.2.1 Langmuir isotherm

The Langmuir adsorption model is based on the assumption that sorption occurs at specific homogeneous sorption sites within the sorbent and intermolecular forces decrease rapidly with the distance from the sorption surface. The model is also based on the assumption that all the sorption sites are energetically identical and sorption occurs on a structurally homogeneous sorbent [19-21]. The equilibrium data for each initial concentration of Cu²⁺ range from 5 to 60 mg/l have been fitted with the Langmuir model (Eq. 1):

$$\frac{C_e}{q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m} \quad (1)$$

where C_e is equilibrium concentration of Cu(II) in solution (mg/l); q_e is the amount of Cu(II) adsorbed onto adsorbents at equilibrium (mg/g); K_L is the Langmuir equilibrium constant related to sorption energy; and q_m is the maximum sorption capacity (mg/g).

A linear plot is gained when C_e/q_e is plotted against C_e for the entire of concentration range of Cu²⁺ studied (Fig. 5). The value of q_m and K_L were calculated from the slopes and the intercepts of lines. The isotherm model will effectively and significantly described the sorption data if R² values ≥ 0.95.

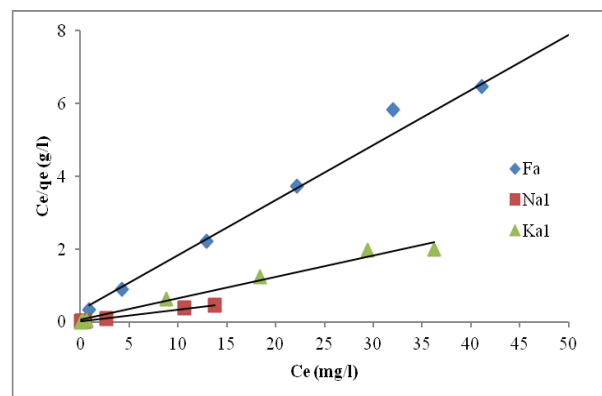


Fig. 5 Langmuir plots for Cu²⁺ ions adsorption onto fly ash and activated fly ash

The adsorption data of Cu²⁺ was found to fit well with the Langmuir isotherm (Table 2). It shows the maximum sorption capacity (q_m) which reflects monolayer coverage of sorbent with sorbate and K_L reflects enthalpy of sorption.

Table 2 Langmuir parameters for Cu²⁺ adsorption onto fly ash and alkali activated fly ash

	Langmuir parameters		R ²
	Q _m (mg/g)	K _L (l/mg)	
FA	6.61	0.45	0.988
NaI	30.21	2.30	0.996
KaI	16.89	0.99	0.979

Raw fly ash usually has low adsorption capacity. Fly ash can be effective adsorbent depending on the composition and treatment if compared with other adsorbent. Activation by alkali treatment would increase the adsorption capacity thus increasing the value for application. Activation by NaOH more effective than by KOH. Regression coefficient (R²) of the plotted isotherm curve shows that the Langmuir isotherm is suitable for all of the fly ashes. Therefore, Cu²⁺ ion adsorption of all of the adsorbent that used in this study was estimated as adsorption on a monolayer and sorption occurs on a structurally homogeneous sorbent.

Langmuir isotherm may be reflected by a dimensionless parameter called separation factor. The dimensionless separation factor (R_L) was calculated from the Langmuir isotherm using the equation:

$$R_L = \frac{1}{1 + K_L C_0} \quad (2)$$

Where K_L is the Langmuir adsorption constant and C₀ is the initial concentration. The R_L values that were in the range of 0 < R_L < 1 for fly ash and activated fly ash (Table 3). Separation factor indicates that isotherm will be according to the following adsorption characteristics: R_L > 1 unfavorable; R_L = 1 corresponds to linear; 0 < R_L < 1 is favorable and R_L = 0 is irreversible. The results show that the separation factor less than 1 suggests a favorable adsorption [21].

Table 3 R_L values calculated at different initial concentrations (mg/l)

Adsorbent	R _L at initial concentration						
	5	10	20	30	40	50	60
FA	0.30	0.16	0.09	0.07	0.05	0.04	0.03
NaI	0.07	0.04	0.02	0.02	0.01	0.01	0.01
KaI	0.15	0.09	0.05	0.03	0.02	0.02	0.02

3.2.2 Freundlich isotherm

This isotherm developed by Freundlich (1926), describes the equilibrium on heterogeneous surface and does not assume monolayer capacity [7, 22]. The isotherm provides an expression involving the surface heterogeneity, exponential distribution of active sites, and

their energies. The Freundlich isotherm can be represented as:

$$\log q_e = \log K_F + \frac{1}{n} \log C_e \quad (3)$$

Where q_e is the amount of Cu(II) ions adsorbed at equilibrium per unit weight of adsorbent (mg/g); C_e is the equilibrium concentration of Cu²⁺ ions in solution (mg/l); and K_F and n are Freundlich constants corresponding to adsorption capacity and intensity respectively. A linear plot is gained when log q_e is plotted against log C_e and the values of K_F and n can be calculated from intercept and slope of the straight line respectively (Fig. 6). The isotherm parameters are summarized at Table 4.

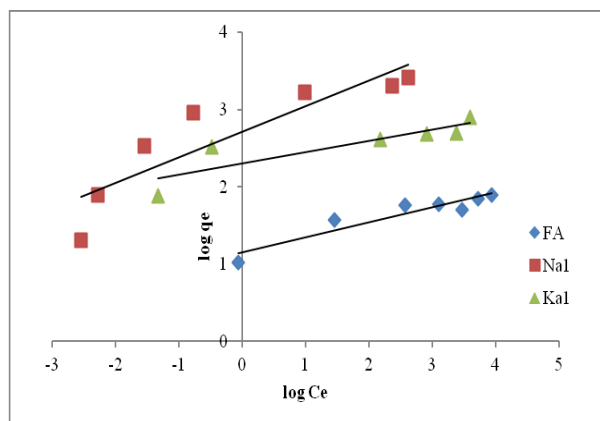


Fig. 6 Freundlich plots for Cu²⁺ ions adsorption onto fly ash and activated fly ash

Table 4 Freundlich parameters for Cu²⁺ adsorption onto fly ash and alkali activated fly ash

	Freundlich parameters		R ²
	K _F (mg/g)	n	
FA	3.16	5.16	0.886
NaI	15.18	3.02	0.798
KaI	8.91	5.18	0.874

It was found that the Freundlich isotherm fits well with Cu²⁺ adsorption by raw fly ash. Furthermore, the adsorption intensity n is > 1 suggesting the existence of a strong bond between adsorbent and adsorbate. Generally, if the exponent lies between 1 < n < 10, it represents advantageous adsorption.

As indicated above, Langmuir model could elucidate the adsorption of Cu²⁺ on the fly ash and fly ash that activated by NaOH as well as KOH since values of R² Langmuir's are larger than Freundlich's for all of the fly ashes. Maximum adsorption capacity of alkali activated by NaOH (30.21 mg/g) is higher than activated by KOH (16.89 mg/g). This result suggests that the adsorption of Cu²⁺ onto fly ash and activated fly ash are monolayer. Similar results were also obtained by others [19, 20, 23].

3.3 Adsorption kinetics

Kinetic models were used to analyze the experimental data regarding the adsorption mechanism and speed

control steps. The adsorption process could be controlled with different kind of mechanisms like mass transfer, diffusion control, chemical reaction, and particle diffusion. Several adsorption models were employed to assess the experimental data. The Lagergren's pseudo first-order and pseudo second-order kinetic models were utilized and fitted with the experimental data for evaluate the adsorption process [24]. Fig. 7 and 8 present the plot of the pseudo first-order and pseudo second-order models for adsorption of Cu^{2+} onto raw fly ash and activated fly ash. Experimental and theoretically calculated adsorption capacities at equilibrium values and coefficients that related to kinetic plots are shown in Table 5.

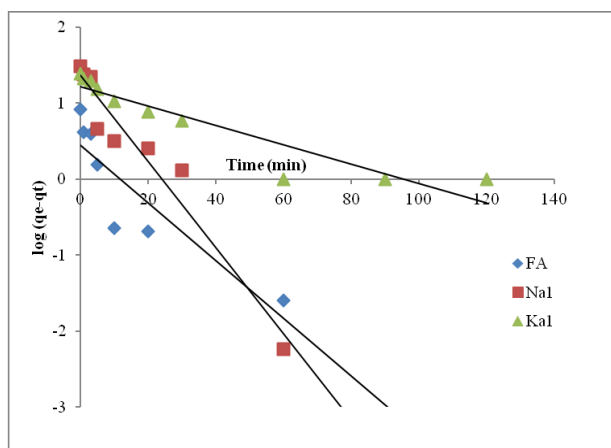


Fig. 7 Fitness of pseudo first-order kinetic

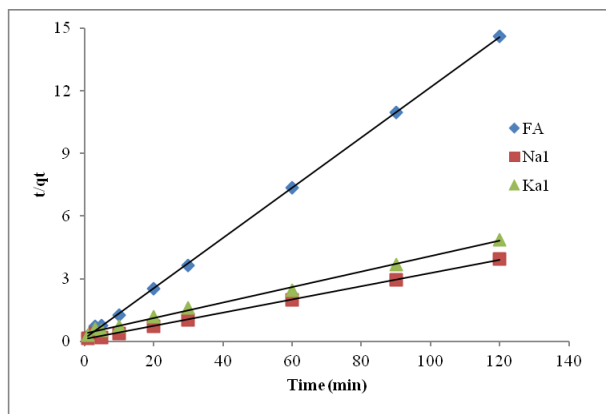


Fig. 8 Fitness of pseudo second-order kinetic

Table 5 Adsorption kinetic model rate constant

	Pseudo first-order			Pseudo second-order			q_{exp} (mg/g)
	q_e (mg/g)	k_1 (min^{-1})	R^2	q_e (mg/g)	k_2 (g/mg/min)	R^2	
Fa	2.8	0.087	0.79	8.31	0.104	0.99	8.2
NaI	23.5	0.131	0.94	31.45	0.009	0.99	30.4
KaI	21.1	0.047	0.94	27.10	0.004	0.99	24.5

As can be seen from Table 5, the linear correlation coefficient for pseudo first-order is not good when compared to the pseudo second-order model. These results indicate that the adsorption of Cu^{2+} ions onto fly ash and activated fly ash is not regarding to first-order reaction. It is obvious from the results of the correlation

coefficient of pseudo second-order model is very high. Also, the theoretical and experimental q_e values are very suitable. This model based on the assumption that the rate limiting step may be a chemical adsorption involving the valence forces through exchange of electrons between the adsorbent and the adsorbate [24, 25].

4 Conclusion

Fly ash is a cheap and effective adsorbent for removal Cu^{2+} ions from aqueous solutions. Changing the nature of fly ash by alkali activated can increase its ability to adsorb Cu^{2+} ions significantly. The increasing of adsorption capacity of fly ash that activated by NaOH was greater than fly ash that activated by KOH. The adsorption of Cu^{2+} ions onto alkali activated fly ash fit the Langmuir isotherm very well as well as the adsorption of Cu^{2+} ions onto fly ash. Maximum adsorption capacities were calculated from the Langmuir isotherm as 30.21 mg/g and 16.89 mg/g for the fly ash that activated by NaOH and KOH respectively. The adsorption of Cu^{2+} ions onto fly ash and alkali activated fly ash follow the pseudo second-order rate kinetics due to being more suitable with experimental data. The adsorption mechanism is a physical process since it contains electrostatic interaction between Cu^{2+} ions and adsorbent.

References

1. T.C. Hsu, C.C. Yu, C.M. Yah, *Fuel*, **87**, 1355–1359 (2008)
2. K.S. Hui, C.Y.H. Chao, S.C. Kot, *Journal of Hazardous Materials*, **B127**, 89-101 (2005)
3. F.A. Lopez, C. Perz, *Journal of Materials Science Letters*, **15**, 1310-13 (1996)
4. M. Ahmaruzzaman, *Colloid and Interface Science*, **166**, 36–59 (2011)
5. K.G. Bhattacharyya, S.S. Gupta, *Advances in Colloid and Interface Science*, **140**, 114-131 (2008)
6. X. Chen, G. Chen, L. Chen, Y. Chen, J. Lehmann, M.B. McBride, A.G. Hay, *Bioresource Technology*, **102**, 8877–8884 (2011)
7. R. Shawabkeh, Al-Harashsheh, Al-Otoom, *Separation and Purification Technology*, **40**, 251-257 (2004)
8. B. Nasernejad, T.E. Zadeh, B.B.Pour, M.E. Bygi, A. Zamani, *Process Biochemistry*, **40**, 1319-1322, (2005)
9. L.P. Lingamdinne, J-K. Yang, Y.Y. Chang, J.R. Koduru, *Hydrometallurgy*, xx, xxx–xxx (2015)
10. Y. Wu, S. Zhang, *Bioresource Technology*, **99** (16), 7709-7715 (2008)
11. X. Guo, S. Zhang, X. Shan, *Journal of Hazardous Materials*, **151** (1), 134-142 (2008)

12. C.H. Weng, C.P. Huang, *Colloids and Surfaces A: Physicochemical Engineering Aspects*, **247**, 137–143 (2004)
13. Y.C. Sharma, Uma, S.N. Upadhyay, C.H. Weng, *Colloids and Surfaces A: Physicochem. Engineering Aspects*, **317**, 222–228 (2008)
14. I. Polowczyk, J. Ulatowska, T. Kozlecki, A. Bastrzyk, W. Sawifiski, *Desalination*, **310**, 93–101 (2013)
15. A. Fernández-Jiménez, A. Palomo, *Cement and Concrete Research*, **35**, 1984–1992 (2005)
16. L. Li, S. Wang, Z. Zhu, *Journal of Colloid and Interface Science*, **300**, 52-59 (2006)
17. M. Visa, *Applied Surface Science*, **263**, 753–762 (2012)
18. M. Kobya, *Bioresource Technology*, **91**, 317–321 (2004)
19. A. Papandreou, C.J. Stournaras, D. Panyas, *Journal of Hazardous Materials*, **148**, 538-547 (2007)
20. M.S. Al-Harashsheh, K. Al-Zboon, L. Al-Makhadmeh, M. Hararah, M. Mahasneh, *Journal of Environmental Chemical Engineering*, **3**, 1669-1677 (2015)
21. S. Mohan, R. Gandhimathi, *Journal of Hazardous Materials*, **169**, 351–359 (2009)
22. S. Wang, L. Li, Z. Zhu, *Journal of Hazardous Materials*, **B139**, 254-259 (2007)
23. H. Xiyili, S. Cetintas, D. Bingol, *Process Safety and Environmental Protection*, **109**, 288-300 (2017)
24. Y.S. Ho, G. McKay, *Process Biochemistry*, **34**, 451–465 (1999)