

Non-linear finite element analysis of reinforced concrete members and punching shear strength of HSC slabs

Kernou Nassim¹, Belakhdar Khalil² and Benyamina Abdelrahmane Bekaddour³

¹ Université Docteur Tahar Moulay Saida , Département de génie civil et hydraulique, Saida, Algérie

² Université de Tamanrasset, Département de science et technologie, Algérie

³ Université Ibnkhalidoun de Tiaret, Département de génie civil, Tiaret, Algérie

Abstract. A rational three-dimensional nonlinear finite element model (NLFEAS) is used for evaluating the behavior of high strength concrete slabs under monotonic transverse load. The non-linear equations of equilibrium have been solved using the incremental-iterative technique based on the modified Newton-Raphson method. The convergence of the solution was controlled by a load convergence criterion. The validity of the theoretical formulations and the program used was verified, through comparison with results obtained using ANSYS program and with available experimental test results. A parametric study was conducted to investigate the effect of different parameters on the behavior of slabs which was evaluated in terms of load-deflection characteristics, concrete and steel stresses and strains, and failure mechanisms. Also, punching shear resistance of slabs was numerically evaluated and compared with the prediction specified by some design codes.

1 Introduction

Reinforced concrete structures present significant nonlinear and accordingly complex behavior and consequently nonlinear analysis of this kind of structure has been subject of research for many years [2]. In the last decades very sophisticated and accurate structural models were proposed, that can take into account most aspects of the nonlinear behavior of concrete structures [7,9].

The complex behavior of concrete slabs under real conditions leads to strong uncertainties related to material properties of slabs and the loading conditions. These uncertainties must be taken into account to be included in the design guidelines of such structures especially when some structure does not fit exactly in any standard due to its size, new material properties, complexity or multidisciplinary nature. In these cases probabilistic analysis can be pursued since design standards are not able to cover the full range of application that engineers are able to conceive.

Most research on the punching shear strength of slabs has been concerned with the generation of experimental data on simply supported slabs and the development of empirical equations. A few analytical analyses have also been proposed by various investigators based on different models. The most known empirical formula for predicting the shear strength of

slabs as result of experimental and analytical studies are those suggested by the ACI-318 code approach.

However, In order to ensure the serviceability requirement of slabs it is necessary to predict the cracking and the deflections of slab structures under service loads. In order to assess the margin of safety of slab structures against failure an accurate estimation of the ultimate load is also essential, in addition to the prediction of the load-deformation behavior of the slab throughout the range of elastic and inelastic response is desirable. The main objectives of this research are: 1-To calibrate and validate the program by comparing the predicted results with available experimental tests and other known software-programs. 2-To study Punching shear behavior and the major material and geometrical parameters that strongly affect it.

2 Finite Element Formulation

For the nonlinear analysis of concrete slabs a nonlinear finite element code NLFEAS (Non-Linear Finite Element Analysis of Slabs) has been used. NLFEAS has been developed to predicate and study the behavior of normal and high strength concrete [9]. Its concept and modeling characteristics are described in the following section.

2.1 Modeling of concrete material in compression

The behavior of concrete in compression is simulated by an elasto-plastic work hardening model up to onset of crushing. The plasticity model and its constituent, and the modeling of concrete under triaxial state of stress, will be discussed in terms of the following elements: 1) Uniaxial stress-strain relationship, 2) Failure criterion, and 3) Crushing condition.

2.1.1. Uniaxial stress-strain relationship

Frequently, the widely used stress-strain relationship of concrete up to the peak stress is given as a parabolic relationship as follows:

$$\sigma = f_c \cdot \left[\frac{2\varepsilon}{\varepsilon_0} - \left(\frac{\varepsilon}{\varepsilon_0} \right)^2 \right] \quad (1)$$

Where ε_0 is the strain at peak stress f_c given by

$$\varepsilon_0 = 2 \cdot \frac{f_c'}{E_c} \quad (2)$$

In the presence of orthogonal cracks which are caused by shear or transverse tensile stresses, concrete exhibits lower compressive strength and stiffness than uniaxially compressed state. Such degradation or softening in compressive strength of concrete is taken into consideration in the present study by multiplying the uniaxial compressive concrete stress defined in Equation (1) by a softening factor λ , as shown in Fig. 1. Among various compression reduction models available in literature, the model suggested by Vecchio, and Aspiotis (1994), is implemented in the present finite element formulation. The model can be expressed as:

$$\lambda = \frac{1}{1 + K_c \cdot K_f} \quad (3)$$

Where: K_c , represents the effect of the transverse cracking and straining, K_f represents the dependence on the strength of the concrete (f_c), K_c and K_f are given by:

$$K_c = 0.27 \left(\frac{\varepsilon_r}{\varepsilon_0} - 0.37 \right) \quad (4)$$

$$K_f = 2.55 - 0.2629 \sqrt{f_c'} \leq 1.11 \quad (5)$$

Where: ε_r is the tensile strain normal to the cracked plane given by:

For cracked sampling point in the principal direction "1"
 $\varepsilon_r = \varepsilon_1$ (6)

For doubly cracked sampling point in both directions "1" and "2"

$$\varepsilon_r = \left(\varepsilon_1^2 + \varepsilon_2^2 \right)^{\frac{1}{2}} \quad (7)$$

Where ε_1 is the transverse tensile strain in the principal direction "1" normal to the cracked plane, ε_2 is the tensile strain in the second direction "2" normal to the second crack plane.

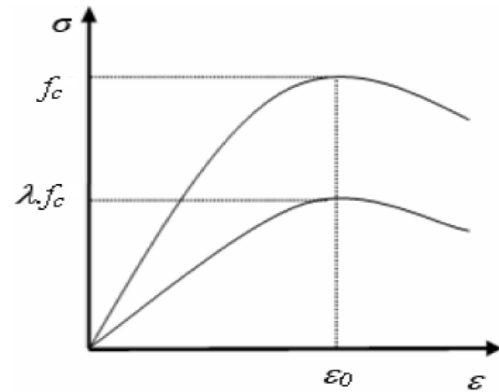


Fig.1. Compression reduction of transversely cracked concrete

2.1.2 Failure criterion

Under triaxial state of stress the failure criterion for concrete is generally assumed to be dependent on three stress invariants. However, the failure criterion used in this study is dependent on two stress invariants which has been proved to be adequate for most practical situations and has been successfully used by many investigators for analyzing reinforced concrete plate and shells which can be expressed as:

$$f(\sigma) = f(I_1, J_2) = \sqrt{\alpha I_1 + 3\beta J_2} - \sigma_0 = 0 \quad (8)$$

Where:

I_1 is the first stress invariant given by:

J_2 is the second deviatoric stress invariant

σ_0 is the equivalent effective stress at the onset of plastic deformation,

$$\alpha = \sigma_0 (\beta - 1) \quad (9)$$

$$\beta = \frac{1 - 2 \cdot \gamma}{\gamma^2 - 2 \cdot \gamma} \quad (10)$$

Where, γ is a constant to be determined from equal biaxial compression state, which is given by:

$$\sigma_x = \sigma_y = -\gamma \sigma_0 \quad (11)$$

The adopted values of γ are taken according to experimental work conducted by Hussein and Marzouk [4] where they found that the constant γ has the values of 19, 14 and 9% for concrete strength of 42.7, 73.7 and 96.5 MPa, respectively.

2.1.3. The crushing condition

The experimental tests of concrete under multiaxial loading indicate that the crushing is a strain related phenomenon, so concrete is considered to crush when the strain reaches a specified ultimate value, after that the current stresses drop suddenly to zero and the concrete is assumed to lose completely its resistance against further deformation. Hence the crushing criterion is directly obtained by using the same form of yield criterion but in terms of strains, as follow:

$$C.I_1 + \sqrt{(C.I_1)^2 + 3 \cdot \beta \cdot J_2} = \epsilon_{cu} \quad (12)$$

Where ϵ_{cu} the ultimate concrete strain that can be obtained from the uniaxial compression test. Frequently, the ultimate concrete crushing strain ϵ_{cu} is estimated to be in the range of 0.0030 as suggested by ACI-318-02 [10] as given by BS8110 [11] and CSA-94 codes [12].

2.2. Modeling of concrete materials in tension

When tensile stress exceeds a limiting value a crack is assumed to form in the plane perpendicular to the direction of that stress and concrete behaves no longer isotropic, and therefore, the normal stiffness is reduced through tension-stiffening concept. Once concrete has cracked, fixed smeared cracking model is used in the current study to model the crack. The gradual release of tensile stresses normal to the cracked plane is represented by bilinear average stress-strain curves to simulate the tension stiffening behavior (Fig.2).

The shear stiffness is also reduced when cracking occurs because it retains the two major mechanisms by which shear is transferred across the crack (the aggregate interlock of the rough crack surfaces and dowel action of the reinforcing bars crossing the crack planes). A bilinear shear retention model is used as shown in Fig. 3. The material parameters used in the analysis are as follow:

Tension stiffening: $\alpha_1 = 5, \alpha_2 = 0.6$

Shear retention: $\gamma_1 = 10, \gamma_2 = 0.5, \gamma_3 = 0.04$

Besides, at onset of cracking Poisson's ratio (ν_c) is set to zero.

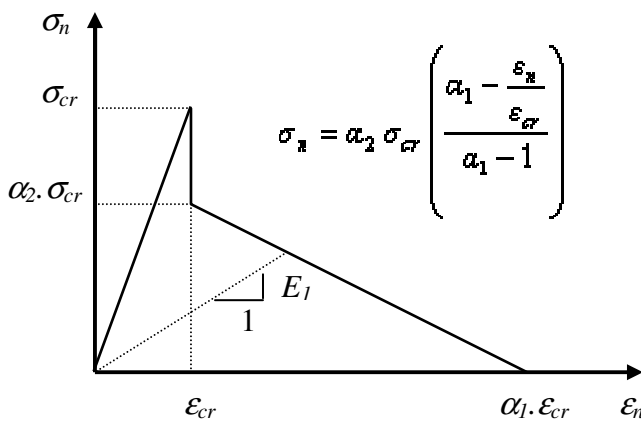


Fig.2. Bilinear average tensile stress-strain of concrete

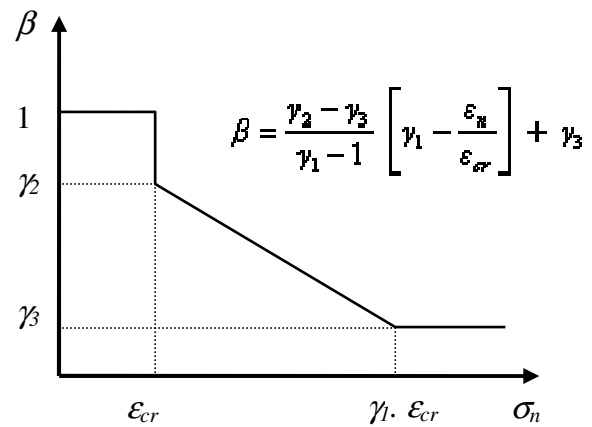


Fig.3. Bilinear shear retention model

2.3. Material modeling of reinforcement

In contrast to concrete, the material modeling of steel is rather simple. Frequently, the steel is modeled using linear elastic-full plastic model, as shown in Fig.4.

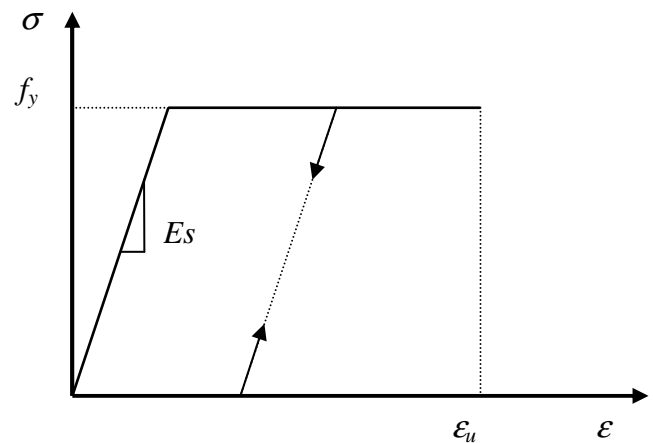


Fig.4. Modeling of steel reinforcing bars

2.4 Finite element idealization

The concrete is represented by using 8-noded brick element. The reinforcing bars are modeled as one dimensional element subjected to axial force only. The non-linear equations of equilibrium have been solved using the incremental-iterative technique based on the modified Newton-Raphson method. The convergence of the solution was controlled by a load convergence criterion. NLEFAS program interface as shown in Fig.5.

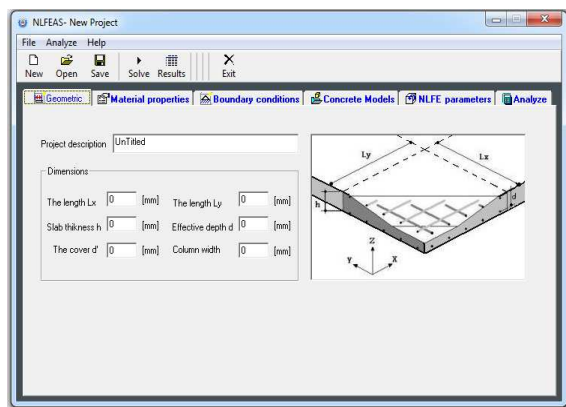


Fig.5. NLFAS program interface

4. Description of selected experimental slab

A simply supported square slabs were selected from an experimental test of reinforced concrete slabs made of HSC, to be used to validate the predicted analytical results and to be used for the reliability analysis. The selected experimental slab was one of eleven slabs carried out by Tmaszewicz [2]. The selected slab was named “ND95-2-3D”, it has span of 2200 mm, with thickness of 240mm. The concrete strength f_c' was 80.3 MPa while the steel yielding stress f_y was 500 MPa. The steel ratio was 2.34 %

The following material properties are assumed in the analysis: $E_s = 200.000\text{MPa}$, $E_c = 3320 \cdot \sqrt{f_c'} + 6900$, $f_t = 0.33 \sqrt{f_c'}$, and $v_c=0.24$.

3 Finite element mesh

The concrete is represented by using 8-noded brick element. The reinforcing bars are modeled as one dimensional element subjected to axial force only, and perfect bond is assumed to occur between the two materials,

By taking advantage of symmetry, a segment representing one quarter of the slabs has been considered in the finite element analysis, noting that the slab was modeled upside down and the loading is applied on the column as shown in Fig.6.

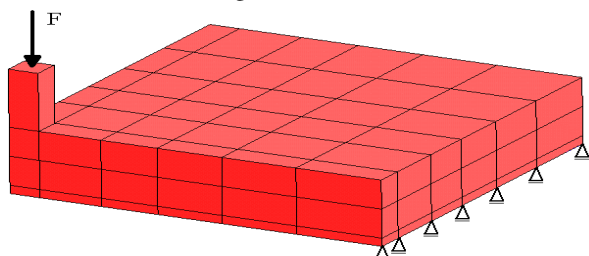


Fig.6. Finite element mesh

4 Validation of the NLFEM program

The results of the present nonlinear finite element analysis of the investigated slabs in terms of ultimate load are compared against the experimental

measurements and listed in Table 1. Fig. 6 shows load-deflection curves of selected slabs of the present finite element analysis and experimental results. According to Fig 6 and Table 1, it can be observed that the present finite element model performs satisfactory and it predicts accurately the real behavior of slabs.

Table 1. Comparison of the predicted and experimental results

Slab	Experimental		FE Analysis		FEA / Exp	
	Ultimate load P_u (KN)	Ultimate deflection D_u (mm)	Ultimate load P_u (KN)	Ultimate deflection D_u (mm)	P_u/P_u	D_u/D_u
ND95-2-3D	1250	7.05	1180	5.84	0.944	0.828
ND115-1-1	2450	11.65	2540	10.29	1.037	0.883

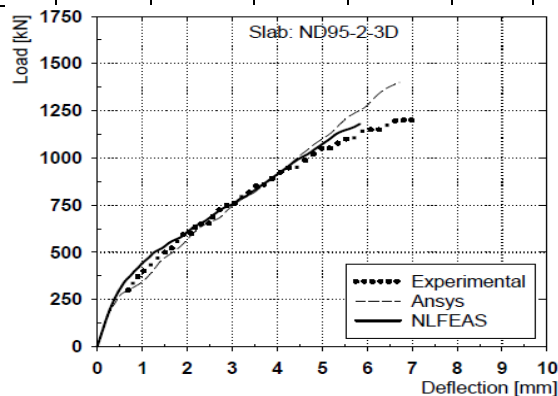


Fig.6. Comparison of predicted and experimental load-deflection curves.

4.1 Effect of compressive strength grade

The concrete compressive strength considered as one of the important primary variables that was studied in the present investigation. The influence of f_c' on the selected slabs' behavior was studied through altering the values of f_c' by different values, and the obtained results are illustrated in Fig.8. It can be seen that generally, the higher the value of f_c' , the higher the expected stiffness and the ultimate load of any slab. It was stated previously that increasing the value of f_c' influences the load-deflection behavior particularly after cracking, but the shape of the load-deflection curve was not highly influenced.

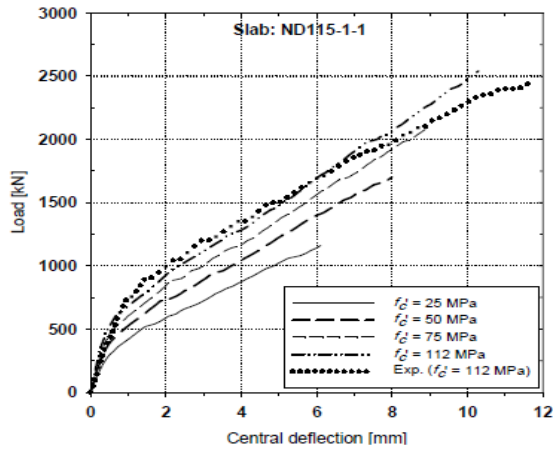


Fig.8. Effect of compressive strength f_c' on the slab response

4.2 Comparison of the experimental punching strength versus present prediction and codes predictions

Experimental results were used to check the validity of the punching shear strength formula given in AS3600 [1], CEB-FIP [3] and NLFEAS [9]. Marzouk and Hussein [4] tested 17 square specimens to investigate the punching shear behaviour of high-strength concrete slabs. Tomaszewicz [2] tested 19 square flat slabs with orthogonal, equally spaced flexural reinforcement and without shear reinforcement. A total of 29 test results from four research studies conducted by Ramdane [8], Hallgren and Kinnunen [6], Marzouk and Hussein [4] and Tomaszewicz [2], were compared to values of punching strength calculated using AS3600. The punching shear strength values specified in different codes vary with concrete compressive strength f_c' and is usually expressed in terms of $f_c'^n$. In AS3600 (Cl. 9.2.3) the punching shear strength is expressed as proportional to $\sqrt{f_c'}$. The ultimate shear strength for slabs without

prestress is given by $V_{uo} = ud(f_{cv})$ where: u = length of the critical perimeter.

$$f_{cv} = \text{punching shear strength (MPa)} \quad (13)$$

$$f_{cv} = 0.17 \left(1 + \frac{2}{\beta_h} \right) \sqrt{f_c'} \leq 0.34 \sqrt{f_c'}$$

β_h : ratio of longest column dimension to shorter column dimension

In CEB-FIP the punching shear resistance, F_{sd} is expressed as proportional to $(f_{ck})^{\frac{1}{3}}$, Where f_{ck} is the characteristic compressive strength of concrete. The highest concrete grade considered in CEB-FIP, which corresponds to f_{ck} equal to 80 MPa. For the calculation of punching load capacity.

$$F_{sd} = 0.18 \xi (100 \rho f_{ck})^{\frac{1}{3}} u_1 d \quad (14)$$

In this study, measured concrete strength is taken as f_{ck} . Fig.9 shows the ratios between test results and the failure loads predicted by different formulae plotted with respect to the concrete strength. The experimental ultimate loads (P_{test}) of the slabs to the values predicted by AS3600 and

CEB-FIP is compared. two points from AS3600 fall below the safety margin with one result for a slab with a concrete strength of 112 MPa. The AS3600 formula can be considered to be applicable up to 100 MPa. However the ratios between observed and calculated loads clearly show that AS3600 is less conservative for the HSC slabs and high scatter is found. Therefore, all above codes and present FE model may be considered applicable for predicting the punching strength of HSC up to 118 MPa.

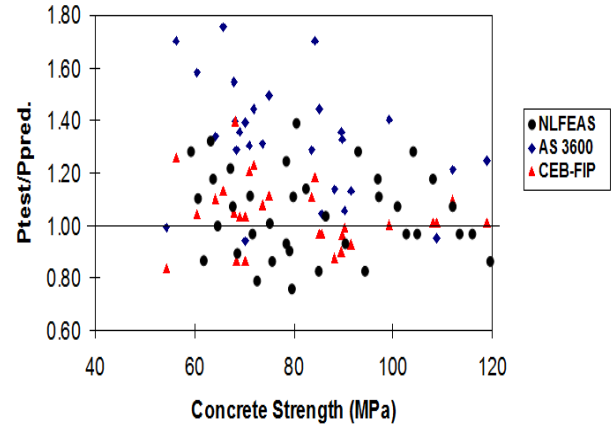


Fig.9. Ratios of experimental and predicted shear strengths

5 Conclusion

The main conclusion extracted from the current study is that the nonlinear finite element method based on advanced 3D models is a powerful and relatively economical tool which can be effectively used to simulate the true behavior of reinforced concrete even under complicated conditions.

The presented finite element program (NLFEAS) is used for the analysis of high strength reinforced concrete slabs subjected to monotonic concentrated loads after calibration using many experimental data. Predictions of the present FE program are compared with valuable experimental data, and the comparisons were judged good. Moreover, the model was able to predict the total response and capacity of the high strength concrete slabs and to indicate the type of failure (flexural or shear).

In AS3600 the punching shear strength is expressed as proportional to $\sqrt{f_c'}$. However in CEB-FIP punching shear strength is assumed to be proportional to $\sqrt[3]{f_c'}$.

The comparison of experimental results show that the AS3600 formula is applicable up to 100 MPa. However the ratios between observed and calculated loads clearly show that AS3600 is less conservative for the HSC slabs. The code of CEB-FIP formula is less conservative for HSC slabs and may be unsafe for some cases.

References

1. AS3600: Concrete Structures Standard. Standards Association of Australia, (1994).
2. A. Tomaszewicz. High-strength Concrete SP2 - Plates and Shells. Report 2.3, Punching Shear Capacity of Reinforced Concrete Slabs. Report No. STF70A93082, SINTEF, Trondheim, (1993).
3. CEB-FIP State-of-the-art report on high-strength concrete. 90/1/1, Bulletin d'Information No. 197, (1990).
4. H.Marzouk, A.Hussein. Experimental Investigation on the Behavior of High Strength Concrete Slabs. ACI structural journal November-December 1991; 88(6) 701-513;(1991).
5. H.Marzouk ,Z. Chen, Z. "Finite Element Analysis of High Strength Concrete Slabs," ACI Structural Journal, V. 90, No. 5, September-October 1993, pp. 505-513; (1993).
6. M.Hallgren, and S.Kinnunen,. Increase of Punching Shear Capacity by using High-Strength Concrete. 4th International Symposium on Utilization of High-strength/High-performance Concrete. Paris, 1996, pp. 1037-1046;(1996).
7. N.Kernou, B.Youcef, K. Belakhdar, K. . Assessment of reliability and punching shear resistance of slabs, GRAĐEVINAR, 67 (11), 1051-1062, (2015) doi: <https://doi.org/10.14256/JCE.1295.2015>.
8. K.E.Ramdane, Punching Shear of High Performance Concrete Slabs. 4th International Symposium on Utilization of High-strength/High-performance Concrete. Paris, 1996, pp. 1015-1026; (1996).
9. M. M. Smadi and K. A. Belakhdar, "Nonlinear finite element analysis of high strength concrete slabs", Computers and Concrete, Vol. 4, No. 3, pp 187-206, (2007).
10. ACI 318-2002. Building Code Requirements for Structural Concrete (ACI 318-02) and Commentary (2002).
11. BS-8110. Structural Use of Concrete, Part 1:Code Practice For Design and Construction,. British Standards Institution, London (1985).
12. CSA, Design of concrete structures for buildings, Standard A23.3- 94, Canadian Standards Association, Rexdale, Ontario,(2004).